

Magnetization of multicomponent ferrofluids

I. Szalai¹ and S. Dietrich^{2,3}

¹Institute of Physics and Mechatronics, University of Pannonia, H-8201 Veszprém,
PO Box 158, Hungary

²Max-Planck-Institut für Intelligente Systeme, Heisenbergstr. 3, D-70569 Stuttgart,
Germany

³Institut für Theoretische und Angewandte Physik, Universität Stuttgart,
Pfaffenwaldring 57, D-70569 Stuttgart, Germany

E-mail: szalai@almos.vein.hu, dietrich@mf.mpg.de

Abstract. The solution of the mean spherical approximation (MSA) integral equation for isotropic multicomponent dipolar hard sphere fluids without external fields is used to construct a density functional theory (DFT), which includes external fields, in order to obtain an analytical expression for the external field dependence of the magnetization of ferrofluidic mixtures. This DFT is based on a second-order Taylor series expansion of the free energy density functional of the anisotropic system around the corresponding isotropic MSA reference system. The ensuing results for the magnetic properties are in quantitative agreement with our canonical ensemble Monte Carlo simulation data presented here.

1. Introduction

Ferrofluids are colloidal suspensions of single domain ferromagnetic grains dispersed in a solvent. The stabilization of such suspensions is usually obtained by coating the magnetic particles with polymer or surfactant layers or by using electric double layer formation. Since each particle of a ferrofluid possesses a permanent magnetic dipole moment, upon integrating out the degrees of freedom of the solvent, which gives rise to effective pair potentials, dispersions of ferrocolloids can be considered as paradigmatic realizations of dipolar liquids [1]. The effective interactions of such magnetic particles are often modeled by dipolar hard-sphere (DHS) [2, 3], dipolar Yukawa [4], or Stockmayer [5] interaction potentials. The most frequently applied methods to describe ferrofluids encompass mean field theories [6, 7], thermodynamical perturbation theory [2], integral equation theories [8, 9, 10], various DFTs [11, 12, 13, 14, 15, 4], as well as Monte Carlo [16, 17] and molecular dynamics [18, 19, 20] simulations.

Within the framework of DFT and the mean spherical approximation (MSA), previously we have proposed an analytical equation [4] for the magnetic field dependence of the magnetization of *one*-component ferrofluids, which turned out to be reliable as compared with corresponding Monte Carlo (MC) simulation data. For this kind of system the effect of an external magnetic field has been taken into account by a DFT

method, which approximates the free energy functional of the anisotropic system with an external field by a second-order Taylor series expansion around the corresponding isotropic reference system without an external field. The expansion coefficients are the direct correlation functions which for the studied isotropic dipolar hard-sphere (DHS) and dipolar Yukawa reference systems can be obtained analytically from Refs. [21, 22].

However, in practice the magnetic colloidal suspensions are often multicomponent. In order to describe the magnetization of ferrofluidic *mixtures* we extend our one-component theory to multicomponent systems. This extension is based on the multicomponent MSA solution obtained by Adelman and Deutch [23]. They showed that the properties of equally sized hard spheres with different dipole moments can be expressed in terms of those of an effective single component system. Because MSA is a linear response theory Adelman and Deutch could predict only the initial slope (or zero-field susceptibility) of the magnetization curve. Using their MSA solutions as those of a reference system, in the following we present DFT calculations of the *full* magnetization curves of equally sized, dipolar hard sphere mixtures. These results are compared with MC simulation data.

2. Microscopic model and MSA solution

We consider dipolar hard-sphere (DHS) fluid mixtures which consist of C components. The constitutive particles have the same diameter σ but the strength m_a of the embedded point dipole can be different for the components $a = 1, \dots, C$. In the following the indices a and b refer to the components while the indices i and j refer to individual particles. The system is characterized by the following pair potential:

$$w_{ij}^{DHS}(\mathbf{r}_{12}, \omega_1, \omega_2) = w_{ij}^{HS}(r_{12}) + w_{ij}^{DD}(\mathbf{r}_{12}, \omega_1, \omega_2), \quad (1)$$

where w_{ij}^{HS} and w_{ij}^{DD} are the hard-sphere and the dipole-dipole interaction pair potential, respectively. The hard-sphere pair potential given by

$$w_{ij}^{HS}(r_{12}) = \begin{cases} \infty & , \quad r_{12} < \sigma \\ 0 & , \quad r_{12} \geq \sigma. \end{cases} \quad (2)$$

The dipole-dipole pair potential is

$$w_{ij}^{DD}(\mathbf{r}_{12}, \omega_1, \omega_2) = -\frac{m_i m_j}{r_{12}^3} D(\omega_1, \omega_2), \quad (3)$$

with the rotationally invariant function

$$D(\omega_1, \omega_2) = 3[\hat{\mathbf{m}}_1(\omega_1) \cdot \hat{\mathbf{r}}_{12}][\hat{\mathbf{m}}_2(\omega_2) \cdot \hat{\mathbf{r}}_{12}] - [\hat{\mathbf{m}}_1(\omega_1) \cdot \hat{\mathbf{m}}_2(\omega_2)], \quad (4)$$

where particle 1 (2) of type i (j) is located at $\mathbf{r}_1$ ($\mathbf{r}_2$) and carries a dipole moment of strength m_i (m_j) with an orientation given by the unit vector $\hat{\mathbf{m}}_1(\omega_1)$ ($\hat{\mathbf{m}}_2(\omega_2)$) with polar angles $\omega_1 = (\theta_1, \phi_1)$ ($\omega_2 = (\theta_2, \phi_2)$); $\mathbf{r}_{12} = \mathbf{r}_1 - \mathbf{r}_2$ is the difference vector between the center of particle 1 and the center of particle 2 with $r_{12} = |\mathbf{r}_{12}|$.

Within the framework of MSA Adelman and Deutch [23] presented an analytical solution for the aforementioned C -component *isotropic* dipolar fluid mixture in the

absence of external fields. The importance of their contribution is that it provides simple analytic expressions for correlation functions, the dielectric constant (in our case the zero-field magnetic susceptibility), and thermodynamic functions. In our envisaged DFT calculations for dipolar mixtures *with* external fields we consider the isotropic DHS fluid mixture without external field as a reference system which is described by the following MSA second-order direct correlation function:

$$c_{ab}^{(2)}(\mathbf{r}_{12}, \omega_1, \omega_2, \rho_1, \dots, \rho_C, T, m_1, \dots, m_C) = c_{HS}^{(2)}(r_{12}, \rho) + \frac{m_a m_b}{\hat{m}^2} \left[c_D^{(2)}(r_{12}, \rho, \hat{n}) D(\omega_1, \omega_2) + c_\Delta^{(2)}(r_{12}, \rho, \hat{n}) \Delta(\omega_1, \omega_2) \right], \quad (5)$$

where $\rho = N/V = \sum_{a=1}^C \rho_a$ is the total number density in the volume V of the system, $\rho_a = N_a/V$ is the number density of species a , $c_{HS}^{(2)}$ is the one-component hard sphere direct correlation function, while $c_D^{(2)}$ and $c_\Delta^{(2)}$ are correlation functions determined by Wertheim [21] for the one-component dipolar MSA fluid at the same temperature but evaluated for an effective dipole moment $m = \hat{m}$ and at an effective packing fraction $\eta = \hat{\eta}$. Accordingly, in Eq. (5) we have introduced

$$\hat{m} = \sqrt{\frac{\sum_{a=1}^C m_a^2}{C}}, \quad \hat{\eta} = \frac{\pi}{6} \sigma^3 \frac{\sum_{a=1}^C m_a^2 \rho_a}{\hat{m}^2} \quad (6)$$

and the rotationally invariant function

$$\Delta(\omega_1, \omega_2) = \hat{\mathbf{m}}_1(\omega_1) \cdot \hat{\mathbf{m}}_2(\omega_2). \quad (7)$$

In order to explain dependence on $\hat{n}$ it is convenient to introduce a new parameter $\hat{\xi} \equiv \hat{\xi}(\hat{\chi}_L) = \hat{\eta} \hat{n}$ which is given by the implicit equation

$$4\pi \hat{\chi}_L = q(2\hat{\xi}) - q(-\hat{\xi}), \quad (8)$$

which has the same form as the corresponding equation for the one-component system (see Refs. [4, 21]) where

$$\hat{\chi}_L = \frac{1}{3} \beta \sum_{a=1}^C \rho_a m_a^2 \quad (9)$$

is the averaged Langevin susceptibility and $\beta = 1/(k_B T)$ is the inverse temperature with the Boltzmann constant k_B . The function $q(x)$ is the reduced inverse compressibility function of hard spheres within the Percus-Yevic approximation:

$$q(x) = \frac{(1 + 2x)^2}{(1 - x)^4}. \quad (10)$$

For the zero-field (initial) magnetic susceptibility χ of the mixture the theory by Adelman and Deutch [23] yields

$$\chi = \frac{\hat{\chi}_L}{q(-\hat{\xi}(\hat{\chi}_L))}. \quad (11)$$

Concerning Eq. (5) Wertheim [21] and Adelman and Deutch [23] showed that

$$c_\Delta^{(2)}(r_{12}, \rho, \hat{n}) = 2\hat{n} [c_{HS}^{(2)}(r_{12}, 2\hat{n}\rho) - c_{HS}^{(2)}(r_{12}, -\hat{n}\rho)], \quad (12)$$

$$c_D^{(2)}(r_{12}, \rho, \hat{n}) = \bar{c}_D^{(2)}(r_{12}, \rho, \hat{n}) - 3r_{12}^{-3} \int_0^{r_{12}} ds s^2 \bar{c}_D^{(2)}(s, \rho, \hat{n}) \quad (13)$$

with

$$\bar{c}_D^{(2)}(r_{12}, \rho, \hat{n}) = \hat{n} [2c_{HS}^{(2)}(r_{12}, 2\hat{n}\rho) + c_{HS}^{(2)}(r_{12}, -\hat{n}\rho)], \quad (14)$$

where $c_{HS}^{(2)}(r_{12}, \rho)$ is the one-component hard sphere Percus-Yevick correlation function at density ρ . The dimensionless quantity $\hat{n} = \hat{\xi}/\hat{\eta}$ is determined by solving Eq. (8). We find that $\hat{n}$ vanishes in the nonpolar limit $m_a \rightarrow 0$ for all a . This can be inferred from the results of Rushbrooke et al. [24] (obtained originally for one-component dipolar fluids) according to which the solution of Eq. (8) can be expressed as a power series in terms of $\hat{\chi}_L$:

$$\hat{\xi} = \frac{\pi}{6} \hat{\chi}_L - \frac{5\pi^2}{48} \hat{\chi}_L^2 + O(\hat{\chi}_L^3). \quad (15)$$

From Eqs. (15) and (6) it follows that

$$\begin{aligned} \lim_{\{m_1, \dots, m_C\} \rightarrow 0} \hat{n} = \\ \lim_{\{m_1, \dots, m_C\} \rightarrow 0} \frac{\hat{\xi}}{\hat{\eta}} = \lim_{\{m_1, \dots, m_C\} \rightarrow 0} (1 + O(\hat{\chi}_L)) \left(\frac{\beta}{3C\sigma^3} \sum_{a=1}^C m_a^2 \right) = 0. \end{aligned} \quad (16)$$

Therefore in this limit the functions $c_D^{(2)}$ and $c_\Delta^{(2)}$ vanish (see Eqs. (12), (13), and (14)). Due to $\frac{m_a m_b}{\hat{m}^2} \leq C \frac{m_a m_b}{m_a^2 + m_b^2} \leq C$, as expected in the nonpolar limit the rhs of Eq. (5) reduces to the direct correlation function $c_{HS}^{(2)}$ of a one-component HS fluid with total density $\rho = \sum_{a=1}^C \rho_a$.

For a one-component system ($C = 1$) the prefactor $m_a m_b / \hat{m}^2$ equals 1 and $\hat{\eta} = \eta = \frac{\pi}{6} \rho \sigma^3$ so that Eqs. (8) and (9) render ξ for the one-component system which indeed yields the one-component direct correlation function.

Considering the case of a binary mixture of hard spheres and of DHS reveals the approximate character of Eq. (5). In this case, for the dipolar hard sphere – hard sphere cross correlations (i.e., $m_a \neq 0$, $m_b = 0$), according to Eq. (5) the corresponding correlation function reduces to the a one-component hard sphere direct correlation function, which certainly is a rough approximation. We note that $c_D^{(2)}(r_{12} \rightarrow \infty) \sim r_{12}^{-3}$ is long-ranged (see Eq. (13)) while $c_\Delta^{(2)}(r_{12} \geq \sigma) = 0$ is short-ranged (see Eq. (12)).

In the following we consider DHS mixtures in a homogeneous external magnetic field $\mathbf{H}$, the direction of which is taken to coincide with the direction of the z axis. For a single dipole the magnetic field gives rise to the following additional contribution to the interaction potential:

$$u_i^{ext} = -\mathbf{m}_i \mathbf{H} = -m_i H \cos \theta_i, \quad (17)$$

where the angle θ_i measures the orientation of the i -th dipole relative to the field direction.

3. Magnetization in an external field

In the following we extend our previous theory [4] to C -component and polydisperse dipolar mixtures in which the particles have the same hard sphere diameter but different strengths of the dipole moments.

3.1. Multicomponent systems

Our analysis is based on the following grand canonical variational functional Ω , which is an extension to C components of the one-component functional used in Ref. [4]:

$$\Omega = F_{DHS}[\rho_1, \dots, \rho_C, \{\alpha_1(\omega), \dots, \alpha_C(\omega)\}, T] - \sum_{a=1}^C \rho_a \int d\omega \alpha_a(\omega) (\mu_a - u_a^{ext}(\omega)), \quad (18)$$

where F_{DHS} is the Helmholtz free energy functional of an anisotropic, dipolar, equally sized hard sphere fluid mixture and where μ_a and $\alpha_a(\omega)$ are the chemical potential and the orientational distribution function of the species a , respectively. Since the external field is spatially constant, $\rho_1, \dots, \rho_C$ are constant, too. Thus F_{DHS} is a function of $\rho_1, \dots, \rho_C, m_1, \dots, m_C$ and a functional of $\alpha_1(\omega), \dots, \alpha_C(\omega)$. The Helmholtz free energy functional consists of the *ideal* gas and the *excess* contribution:

$$F_{DHS} = F^{id}[\rho_1, \dots, \rho_C, \{\alpha_1(\omega), \dots, \alpha_C(\omega)\}, T] + F_{DHS}^{exc}[\rho_1, \dots, \rho_C, \{\alpha_1(\omega), \dots, \alpha_C(\omega)\}, T]. \quad (19)$$

For the C -component mixture the ideal gas contribution has the form

$$F^{id} = k_B T V \sum_{a=1}^C \rho_a \left[\ln(\rho_a \Lambda_a) - 1 + \int d\omega \alpha_a(\omega) \ln(4\pi \alpha_a(\omega)) \right], \quad (20)$$

where Λ_a is the de Broglie wavelength of species a . If the system is *anisotropic* the DHS free energy $F_{DHS}^{exc, ai}$ is approximated by a second-order functional Taylor series, expanded around a homogeneous *isotropic* reference system with bulk densities $\rho_1, \dots, \rho_C$ and an isotropic free energy $F_{DHS}^{exc, i}$:

$$\begin{aligned} \beta F_{DHS}^{exc, ai}[\rho_1, \dots, \rho_C, \{\alpha_1(\omega), \dots, \alpha_C(\omega)\}, T] &= \beta F_{DHS}^{exc, i}(\rho_1, \dots, \rho_C, T) \\ &- \sum_{a=1}^C \rho_a \int d^3 r_1 d\omega \Delta \alpha_a(\omega) c_a^{(1)}(\rho_1, \dots, \rho_C, T) \\ &- \frac{1}{2} \sum_{a,b=1}^C \rho_a \rho_b \int d^3 r_1 d\omega_1 \int d^3 r_2 d\omega_2 \Delta \alpha_a(\omega_1) \Delta \alpha_b(\omega_2) c_{ab}^{(2)}(\mathbf{r}_{12}, \omega_1, \omega_2, \rho_1, \dots, \rho_C, T), \end{aligned} \quad (21)$$

where $\Delta \alpha_a(\omega) = \alpha_a(\omega) - 1/(4\pi)$ is the difference between the anisotropic ($H \neq 0$) and the isotropic ($H = 0$) orientational distribution function of the component a ; $c_a^{(1)}$ and $c_{ab}^{(2)}$ (see Eq.(5)) are the first- and second-order direct correlation functions, respectively, of the components of the *isotropic* DHS mixtures. Since in the isotropic system all $c_a^{(1)}$ are independent of the dipole orientation ω , and because $\int d\omega \Delta \alpha_a(\omega) = 0$, only the second-order direct correlation functions $c_{ab}^{(2)}$ provide a nonzero contribution to the

above free energy functional. Since $c_{ab}^{(2)}$ depends only on the difference vector $\mathbf{r}_1 - \mathbf{r}_2$, Eq.(21) reduces to

$$\begin{aligned} \beta F_{DHS}^{exc,ai}[\rho_1, \dots, \rho_C, \{\alpha_1(\omega), \dots, \alpha_C(\omega)\}, T] &= \beta F_{DHS}^{exc,i}(\rho_1, \dots, \rho_C, T) \\ -\frac{1}{2}\rho^2 V \sum_{a,b=1}^C x_a x_b \int d\omega_1 \int d\omega_2 \Delta\alpha_a(\omega_1) \Delta\alpha_b(\omega_2) \int d^3r_{12} c_{ab}^{(2)}(\mathbf{r}_{12}, \omega_1, \omega_2, \rho_1, \dots, \rho_C, T), \end{aligned} \quad (22)$$

where $x_a = N_a/N = \rho_a/\rho$ is the mole fraction of the component a . The expression for the excess free energy $\beta F_{DHS}^{exc,i}$ of the isotropic DHS system was also given by Adelman and Deutch [23]. In the case of a cylindrical sample (elongated around the magnetic field direction) and homogeneous magnetization all $\alpha_a(\omega)$ depend only on the polar angle θ , and thus they can be expanded in terms of Legendre polynomials:

$$\alpha_a(\omega) = \frac{1}{2\pi} \bar{\alpha}_a(\cos \theta) = \frac{1}{2\pi} \sum_{l=0}^{\infty} \alpha_{al} P_l(\cos \theta), \quad a = 1, 2, \dots, C. \quad (23)$$

Due to $\alpha_{a0} = 1/2$ one has

$$\Delta\alpha_a(\omega) = \frac{1}{2\pi} \sum_{l=1}^{\infty} \alpha_{al} P_l(\cos \theta). \quad (24)$$

The second-order MSA direct correlation functions of the DHS fluid mixture (see Eq. (5)) are used to obtain the excess free energy functional. In order to avoid depolarization effects due to domain formation, we consider sample shapes of thin cylinders, i.e., needle-shaped volumes V . Due to the properties of D , Δ , and P_l only the terms α_{al} with $l \leq 1$ contribute to the *excess* free energy. Elementary calculation leads to

$$\frac{F_{DHS}^{exc,ai}}{V} = f_{DHS}^{exc,i} - \frac{2\rho^2}{9\hat{\chi}_L} (1 - q(-\hat{\xi})) \sum_{a,b=1}^C x_a x_b m_a m_b \alpha_{a1} \alpha_{b1}, \quad (25)$$

where $f_{DHS}^{exc,i} = F_{DHS}^{exc,i}/V$. Minimization of the grand canonical functional with respect to the orientational distribution functions (note that $f_{DHS}^{exc,i}$ does not depend on them) yields

$$\bar{\alpha}_a(\omega) = Z_a^{-1} \exp \left(\beta m_a \left(H + \frac{2\rho}{3\hat{\chi}_L} (1 - q(-\hat{\xi})) \sum_{b=1}^C x_b m_b \alpha_{b1} \right) P_1(\cos \theta) \right), \quad (26)$$

with normalization constants Z_a which are fixed by the requirements $\int d\omega \alpha_a(\omega) = 1$. With this normalization the expansion coefficients α_{a1} are given by

$$\alpha_{a1} = \frac{3}{2} L \left[\beta m_a \left(H + \frac{2(1 - q(-\hat{\xi}))}{3\hat{\chi}_L} \sum_{b=1}^C \rho_b m_b \alpha_{b1} \right) \right], \quad a = 1, 2, \dots, C, \quad (27)$$

where $L(x) = \coth(x) - 1/x$ is the Langevin function. Each particle of the magnetic fluid carries a dipole moment which will be aligned preferentially in the direction of the external field. This gives rise to a magnetization

$$M = \sum_{a=1}^C \rho_a m_a \int d\omega \alpha_a(\omega) \cos \theta = \frac{2}{3} \sum_{a=1}^C \rho_a m_a \alpha_{a1}. \quad (28)$$

Equations (28) and (27) lead to an implicit equation for the dependence of the magnetization on the external field:

$$M = \rho \sum_{a=1}^C m_a x_a L \left[\beta m_a \left(H + \frac{(1 - q(-\hat{\xi}))}{\hat{\chi}_L} M \right) \right]. \quad (29)$$

We note that in Eq. (29) in the limit of weak fields the series expansion of the Langevin function, $L(x \rightarrow 0) = x/3$, reduces to Eq. (11) for the zero-field magnetic susceptibility.

3.2. Polydisperse systems

For ferromagnetic grains the dipole moment of a particle is given by

$$m(x) = \frac{\pi}{6} M_s \mathcal{D}^3, \quad (30)$$

where M_s is the bulk saturation magnetization of the core material and $\mathcal{D}$ is the diameter of the particle. Accordingly, our model of equally sized particles with different dipole moments applies to systems composed of materials with distinct saturation magnetizations. Another possibility consists of considering particles with a magnetic core and a nonmagnetic shell, which allows one to vary m via changing the core size with M_s fixed and by keeping the overall diameter of the particles fixed via adjusting the thickness of the shell. For a small number C of components this can be experimentally realizable.

Equation (11) has been extended even to the description of polydisperse ferrofluids [9, 19]. However, it is unlikely that this extension relates to a realistic experimental system because it supposes again that the diameters of all particles are the same. The two possible realizations mentioned above will be very difficult to implement for a large number C of components, mimicking polydispersity. If one nonetheless wants to study such kind of a system the expression for its zero-field susceptibility is a natural extension of Eq. (9):

$$\bar{\chi}_L = \frac{1}{3} \beta \rho \int_0^\infty d\mathcal{D} p(\mathcal{D}) m^2(\mathcal{D}), \quad (31)$$

where $p(\mathcal{D})$ is the probability distribution function for the magnetic core diameter. The corresponding zero-field susceptibility of the polydisperse system is

$$\bar{\chi} = \frac{\bar{\chi}_L}{q(-\bar{\xi}(-\bar{\chi}_L))}, \quad (32)$$

where $\bar{\xi}$ is the implicit solution of the equation

$$4\pi\bar{\chi}_L = q(2\bar{\xi}) - q(-\bar{\xi}). \quad (33)$$

We note that similarly the above equation for the magnetization (see Eq. (29)) can also be extended to polydisperse fluids leading to magnetization curves $\bar{M}(H)$ defined implicitly by

$$\bar{M} = \rho \int_0^\infty d\mathcal{D} p(\mathcal{D}) m(\mathcal{D}) L \left[\beta m(\mathcal{D}) \left(H + \frac{(1 - q(-\bar{\xi}))}{\bar{\chi}_L} \bar{M} \right) \right]. \quad (34)$$

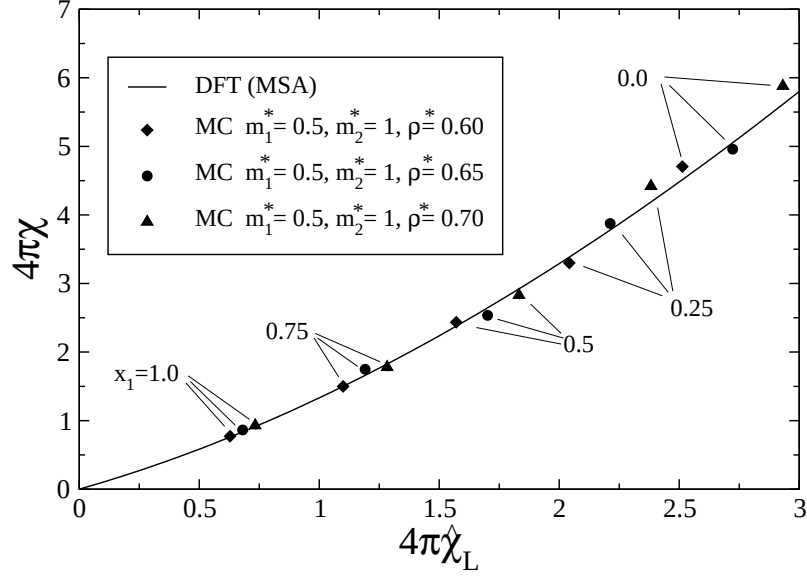


Figure 1. Zero-field susceptibility χ (Eq. (11)) as function of the averaged Langevin susceptibility $\hat{\chi}_L \sim 1/T$ (Eq. (9)). In terms of these quantities DFT (MSA) predicts the master curve given by the full line. The MC data correspond to the following choices of the system parameters. The dipole moments are $m_1^* = 0.5$ and $m_2^* = 1$ in all cases, the reduced densities are $\rho^* = 0.6$ (diamonds), $\rho^* = 0.65$ (circles), and $\rho^* = 0.7$ (triangles) with the concentrations $x_1 = 0$, $x_1 = 0.25$, $x_1 = 0.5$, $x_1 = 0.75$, and $x_1 = 1$. The error bars of the MC data are given by the symbol sizes.

In the limit of weak fields Eq. (34) reduces to the expression in Eq. (32) for the zero-field susceptibility. In the following we shall do not assess via MC simulations the range of validity of Eq. (34) for polydisperse magnetic fluids, leaving this for future studies.

4. Monte Carlo simulations

In order to assess the predictions of the DFT presented in Sec. 3 we have carried out MC simulations for DHS fluid mixtures using canonical (NVT) ensembles. Boltzmann sampling and periodic boundary conditions with the minimum-image convention [25] have been applied. A spherical cutoff of the dipole-dipole interaction potential at half of the linear extension of the simulation cell has been applied and the reaction field long-ranged correction [25] with a conducting boundary condition has been adopted. For obtaining the magnetization data, after 40.000 equilibration cycles 0.8-1.0 million production cycles have been used involving 1024 particles. In the simulations with an applied field the equilibrium magnetization is obtained from the equation

$$\mathbf{M} = \frac{1}{V} \left\langle \sum_{i=1}^N \mathbf{m}_i \right\rangle, \quad (35)$$

where the brackets denote the ensemble average. In simulations without external field the zero-field magnetic susceptibility has been obtained from the corresponding

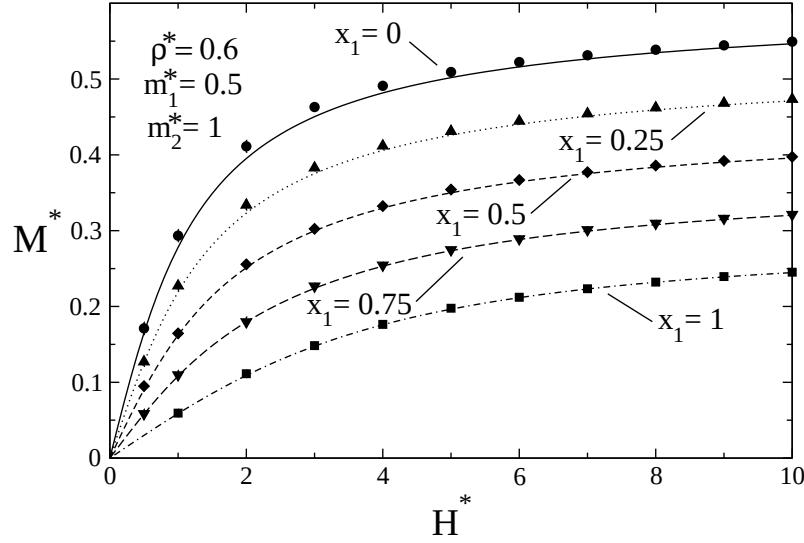


Figure 2. Magnetization curves of a binary DHS fluid mixture for five values of the concentration x_1 of the species with $m_1^* = 0.5$; $m_2^* = 1$. The overall number density is $\rho^* = 0.6$. The curves correspond to the predictions of the MSA based DFT (Eq. (29)). The symbols are MC simulation data. Their error bars are given by the symbol sizes.

fluctuation formula

$$\chi = \frac{\beta(\langle \mathcal{M}^2 \rangle - \langle \mathcal{M} \rangle^2)}{3V}, \quad (36)$$

where $\mathcal{M} = \sum_{i=1}^N \mathbf{m}_i$ is the instantaneous magnetic dipole moment of the system. Statistical errors have been determined from the standard deviations of subaverages encompassing 100.000 MC cycles.

5. Numerical results and discussion

In the following we shall use reduced quantities: $\rho^* = \rho\sigma^3$ as the reduced density, $m_a^* = m_a/\sqrt{k_B T \sigma^3}$ as the dimensionless dipole moment of species a , $H^* = H\sqrt{\sigma^3/(k_B T)}$ as the reduced magnetic field strength, and $M^* = M\sqrt{\sigma^3/(k_B T)}$ as the reduced magnetization. The calculation of the zero-field susceptibility and the magnetization $M(H)$ of the multicomponent DHS fluid mixtures (with identical particle diameters but different dipole moments) can be summarized by the sequence of the following steps:

- 1) calculation of the Langevin susceptibility according to Eq. (9),
- 2) solving Eq. (8) for $\hat{\xi}$,
- 3) calculation of the zero-field susceptibility according to Eq. (11),
- 4) calculation of the magnetization for a given value of H according to Eq. (29) using the consecutive approximation method with $M = 0$ as initial value. The convergence of this consecutive approximation is very good, obtaining the limiting results within 5-8 cycles.

Figure 1 shows the dependence of the zero-field susceptibility χ on the Langevin

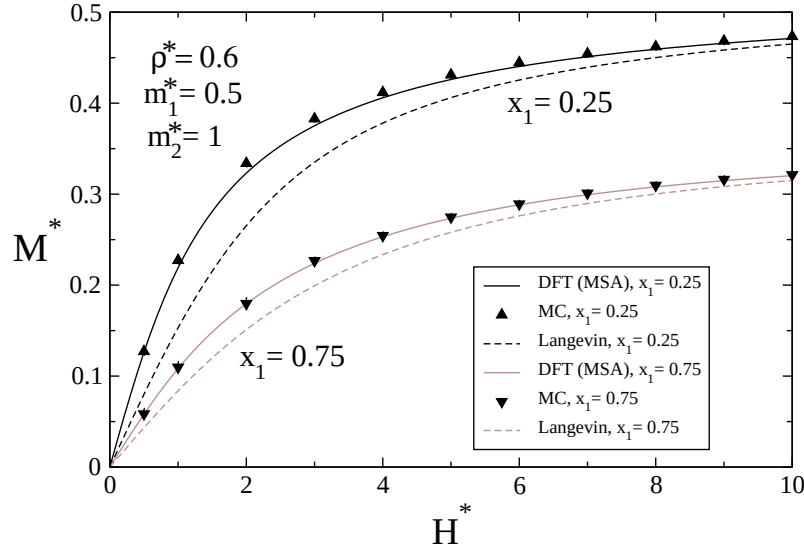


Figure 3. Same system as in Fig. 2. For $x_1 = 0.25$ and $x_1 = 0.75$ DFT (MSA) and the corresponding MC data are compared with the Langevin magnetization curves. The error bars of the MC data are given by the symbol sizes.

susceptibility $\chi_L \sim 1/T$ (see Eq. (9)) for dipolar hard sphere mixtures as obtained from Eq. (11) and from the numerical solution of Eq. (8). This result is compared with MC simulation data for a binary mixture $[(m_1^*, m_2^*) = (0.5, 1)]$ for three total number densities ρ^* and five concentrations x_1 . In these cases DFT (MSA) provides a good approximation for the initial susceptibility of this binary system within the range $0 \leq 4\pi\chi_L \lesssim 2.5$. Within this range the two-component system with various concentrations and densities can be described by the same master curve which is the same also for different systems $(m_1^*, m_2^*, \dots, m_C^*)$. This is the main statement of the MSA theory by Adelman and Deutch [23].

Figure 2 displays the magnetization curves of the two-component DHS fluid mixture with $(m_1^*, m_2^*, \rho^*) = (0.5, 1, 0.6)$ for five values of the concentration. For high values of H^* we find excellent, quantitative agreement for all concentrations between the DFT (MSA) results and the MC data. For small values of H^* , especially for $H^* = 0.5$, i.e., in the linear response regime, the agreement between the simulation data and the DFT results is also very good, which matches with the good agreement found for the zero-field susceptibility (see Fig. 1). Close to the elbow of the magnetization curves the level of quantitative agreement reduces significantly for smaller concentrations x_1 of the magnetically weaker component, while it remains good for large concentrations x_1 . We note that also for two-dimensional systems this range is the most sensitive one concerning the agreement between theoretical results and simulation data [26]. For the same system Fig. 3 displays a comparison between the DFT results together with the MC data and the corresponding Langevin theory. This shows that the interparticle interaction enhances the magnetization relative to the corresponding values of the Langevin theory. For a three-component DHS fluid mixture $[(m_1^*, m_2^*, m_3^*) = (0.5, 0.75, 1)]$ Fig. 4 displays

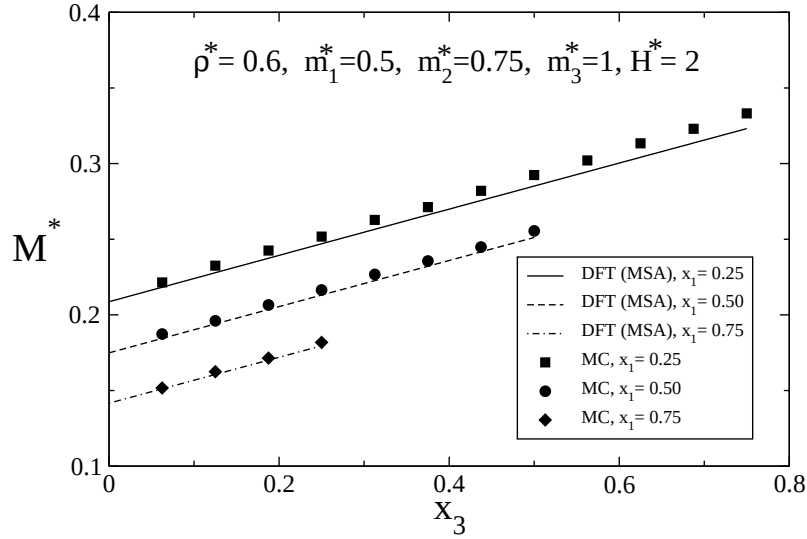


Figure 4. Dependence of the magnetization on the concentration x_3 of the species with $m_3^* = 1$ for a three-component DHS fluid mixture for a fixed field strength $H^* = 2$ and concentrations $x_1 = 0.25$, $x_1 = 0.5$, and $x_1 = 0.75$; $x_1 + x_2 + x_3 = 1$. The reduced dipole moments of the species 1 and 2 are $m_1^* = 0.5$ and $m_2^* = 0.75$. The overall number density is $\rho^* = 0.6$. The error bars of the MC data are given by the symbol sizes.

the dependence of the magnetization on the concentration x_3 for a fixed field strength $H^* = 2$ and for three values of the concentration x_1 ; $x_1 + x_2 + x_3 = 1$. Since the value $H^* = 2$ falls into the aforementioned elbow regime of the magnetization curves, for the small concentration $x_1 = 0.25$ of the less polar ($m_1^* = 0.5$) component the DFT (MSA) results underestimate the simulation data. At higher concentrations of x_1 the agreement between DFT and the simulation data is much better. This is expected to occur, because for large x_1 the fluid is dominated by less polar particles.

6. Summary

We have obtained the following main results:

- 1) Based on a second-order Taylor series expansion of the anisotropic free energy functional of equally sized dipolar hard spheres with different dipole moments and by using the mean spherical approximation (MSA) we have derived an analytical expression (Eq. (29)) for the magnetization of multicomponent ferrofluidic mixtures in external fields. This implicit equation extends the applicability of MSA to the presence of external magnetic fields of arbitrary strengths. We find quantitative agreement between the results from this DFT (MSA) and our Monte Carlo simulation data for Langevin susceptibilities $4\pi\chi_L \lesssim 2.5$ (Figs. 2, 3, and 4).
- 2) As confirmed also by MC simulation data the zero-field susceptibility of multicomponent ferrofluids can be expressed by a single master curve in terms of the Langevin susceptibility (Fig. 1). Beyond the linear response regime the magnetization

curves of multicomponent ferrofluids cannot be reduced to a single master curve (Eq. (29)).

3) By applying the MSA theory for the magnetic susceptibility to polydisperse systems we have extended the multicomponent magnetization equation to polydisperse systems.

Acknowledgments

I. Szalai acknowledges financial support for this work by the Hungarian State and the European Union within the project TAMOP-4.2.1/B-09/1/KONV-2010-0003.

References

- [1] Huke B and Lücke M 2004 *Rep. Prog. Phys.* **67**, 1731
- [2] Ivanov A O and Kuznetsova O B 2001 *Phys. Rev. E* **64**, 041405
- [3] Buyevich Y A and Ivanov A O 1992 *Physica A* **190**, 276
- [4] Szalai I and Dietrich S 2008 *J. Phys.: Condensed Matter* **20**, 204122
- [5] Russier V and Douzi M 1994 *J. Colloid Interface Sci.* **162**, 356
- [6] Debye P 1912 *Z. Phys.* **13**, 97
- [7] Sano K and Doi M 1983 *J. Phys. Soc. Jpn.* **52**, 2810
- [8] Martin G A R, Bradbury A and Chantrell R W 1987 *J. Magn. Magn. Mat.* **65**, 177
- [9] Morozov K I and Lebedev A V 1990 *J. Magn. Magn. Mater.* **85**, 51
- [10] Klapp S H L and Forstmann F 1999 *Phys. Rev. E* **60**, 3183
- [11] Teixeira P I and Telo da Gama M M 1991 *J. Phys.: Condensed Matter* **3**, 111
- [12] Frodl P and Dietrich S 1992 *Phys. Rev. A* **45**, 7330
- [13] Groh B and Dietrich S 1994 *Phys. Rev. E* **50**, 3814
- [14] Groh B and Dietrich S 1996 *Phys. Rev. E* **53**, 2509
- [15] Szalai I and Dietrich S 2009 *Eur. Phys. J. E* **28**, 347
- [16] Kristóf T and Szalai I 2003 *Phys. Rev. E* **68**, 041109
- [17] Trasca R A and Klapp S H L 2008 *J. Chem. Phys.* **129**, 084702
- [18] Holm C and Weis J J 2005 *Curr. Opin. Colloid Inter. Sci.* **10**, 133
- [19] Ivanov A O, Kantorovich S S, Reznikov E N, Holm C, Pshenichnikov A F and Lebedev A V 2007 *Phys. Rev. E* **75**, 061405
- [20] Jordanovic J and Klapp S H L 2009 *Phys. Rev. E* **79**, 021405
- [21] Wertheim M S 1971 *J. Chem. Phys.* **55**, 4291
- [22] Henderson D, Boda D, Chan K-Y and Szalai I 1999 *J. Chem. Phys.* **110**, 7348
- [23] Adelman S A and Deutch J M 1973 *J. Chem. Phys.* **59**, 3971
- [24] Rushbrooke G S, Stell G and Høye J S 1973 *Molec. Phys.* **26**, 1199
- [25] Allen M P and Tildesley D J, *Computer Simulation of Liquids* (Clarendon, Oxford, 2001)
- [26] Kristóf T and Szalai I 2008 *J. Phys.: Condensed Matter* **20**, 204111